Australian Wool Testing Authority Ltd - trading as AWTA Product Testing A.B.N 43 006 014 106 1st Floor, 191 Racecourse Road, Flemington, Victoria 3031 P.O Box 240, North Melbourne, Victoria 3051

Phone (03) 9371 2400 Fax (03) 9371 2499

#### **TEST REPORT**

AWTA PRODUCT TESTING

Client :	Woven Image Pty Ltd	Test Number	:	19-006865
	37-39 Chard Road	Issue Date	:	17/12/2019
	Brookvale NSW 2100	Print Date	:	18/12/2019

Sample Description	Clients Ref : "Wave Dune" Non-woven acoustic wallcovering
	Colour : Off White
	End Use : Wallcovering
	Nominal Composition : 100% Polyester (45% Recycled)
	Nominal Mass per Unit Area/Density : Approx 1378g/m2
	Nominal Thickness : Approx 3mm
AS/NZS 3837-1998	Method of Test for Heat and Smoke Release Rates for Materials and Products using an Oxygen
	Consumption Calorimeter

Chaoiman

Date Tested 17/12/2019 Operator AWTA Test Operator 2 Face Tested Face

			Specimen			
		1	2	3	Mean	
Average Heat Release Rate		70.0	65.7	73.2	69.6	kW/m²
Average Specific extinction area		265.1	189.3	218.6	224.3	m²/kg
		(according to Specificat	ion C1.10 of the	Building Code of	Australia)	
Test orientation :	Horizontal		Specimen			
			•	•		

	1	2	3	Mean	
Irradiance	50	50	50	50	kW/m²
Exhaust flow rate	0.024	0.024	0.024	0.024	m³/s
Time to sustained flaming	77	84	69	77	sec
Test duration	574	588	587	583	sec
Peak heat release after ignition	270.6	253.8	315.6	280.0	kW/m²
Average heat at 60 s	165.4	153.6	160.7	159.9	kW/m²

#### Australian Wool Testing Authority Ltd Copyright - All Rights Reserved C

118581

40718

Accredited for compliance with ISO/IEC 17025 - Testing

- Mechanical Testing - Performance & Approvals Testing

- Chemical Testing Accreditation No. : Accreditation No : Accreditation No.

Samples and their identifying descriptions have been provided by the client unless otherwise stated. AWTA Ltd makes no warranty, implied or otherwise, as to the source of the tested samples. The above test results relate only to the sample or samples tested. This document shall not be reproduced except in full and shall be rendered void if amended or altered. This document, the names AWTA Product Testing and AWTA Ltd may be used in advertising providing the content and format of the advertisement have been approved by the Managing Director of AWTA Ltd.

12

983

985

1356



Page 1 of 8



AWTA Product Testing

Australian Wool Testing Authority Ltd - trading as AWTA Product Testing A.B.N 43 006 014 106 1st Floor, 191 Racecourse Road, Flemington, Victoria 3031 P.O Box 240, North Melbourne, Victoria 3051

Phone (03) 9371 2400 Fax (03) 9371 2499

### **TEST REPORT**

Client :	Woven Image Pty Ltd 37-39 Chard Road Brookvale NSW 2100			Issu	Number : e Date : : Date :	19-006865 17/12/2019 18/12/2019
Average heat a	at 180 s	149.5	136.1	153.4	146.3	kW/m²
Average heat a	at 300 s	105.9	98.1	110.1	104.7	kW/m²
Total heat relea	ased	34.6	33.1	38.0	35.2	MJ/m²
Average effect	ive heat of combustion	11.2	11.5	12.2	11.6	MJ/kg
Initial thicknes	S	10	10	10	10.0	mm
Initial mass		98.6	98.2	97.4	98.1	g
Mass at sustai	ned flaming	97.8	97.4	97.1	97.4	g
Mass remainin	g	73.4	74.7	71.7	73.3	g
Mass percenta	age pyrolysed	25.6	23.9	26.4	25.3	%
Mass loss		3.1	2.9	3.2	3.1	kg/m²
Average rate of	of mass loss	6.3	5.7	6.0	6.0	g/m².s
Additional Obs	servations	None				
Difficulties End	countered during Testing	None				

These test results relate only to the behaviour of the product under the conditions of the test, they are not intended to be the sole criterion for assessment of performance under real fire conditions.

The results of these fire tests may be used to directly assess fire hazard, but it should be recognised that a single test method will not provide a full assessment of the fire hazard under all fire conditions.

Samples were loose laid onto a substrate of 6mm thick cement sheeting prior to testing.

Tests were conducted with a wire grid placed over the sample during testing. This was done to contain intumescing sample within the sample holder.

118581

40718

Australian Wool Testing Authority Ltd Copyright - All Rights Reserved C



Accredited for compliance with ISO/IEC 17025 - Testing - Chemical Testing - Mechanical Testing - Performance & Approvals Testing

Accreditation No Accreditation No 985 : Accreditation No. 1356

983

Samples and their identifying descriptions have been provided by the client unless otherwise stated. AWTA Ltd makes no warranty, implied or otherwise, as to the source of the tested samples. The above test results relate only to the sample or samples tested. This document shall not be reproduced except in full and shall be rendered void if amended or altered. This document, the names AWTA Product Testing and AWTA Ltd may be used in advertising providing the content and format of the advertisement have been approved by the Managing Director of AWTA Ltd.

10

Page 2 of 8





Australian Wool Testing Authority Ltd - trading as AWTA Product Testing A.B.N 43 006 014 106 1st Floor, 191 Racecourse Road, Flemington, Victoria 3031

P.O Box 240, North Melbourne, Victoria 3051

Phone (03) 9371 2400 Fax (03) 9371 2499


### TEST REPORT

Client : Woven Image Pty Ltd 37-39 Chard Road Brookvale NSW 2100 
 Test Number
 :
 19-006865

 Issue Date
 :
 17/12/2019

 Print Date
 :
 18/12/2019

Specimen: 1

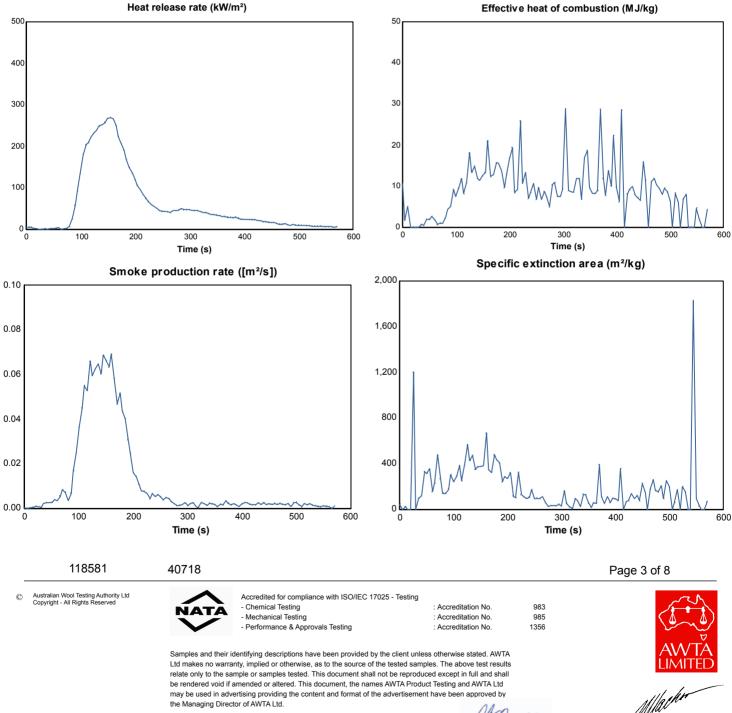

10

Australian Wool Testing Authority Ltd - trading as AWTA Product Testing A.B.N 43 006 014 106 1st Floor, 191 Racecourse Road, Flemington, Victoria 3031

P.O Box 240, North Melbourne, Victoria 3051


Phone (03) 9371 2400 Fax (03) 9371 2499

### **TEST REPORT**

Client : Woven Image Pty Ltd 37-39 Chard Road Brookvale NSW 2100 
 Test Number
 :
 19-006865

 Issue Date
 :
 17/12/2019

 Print Date
 :
 18/12/2019

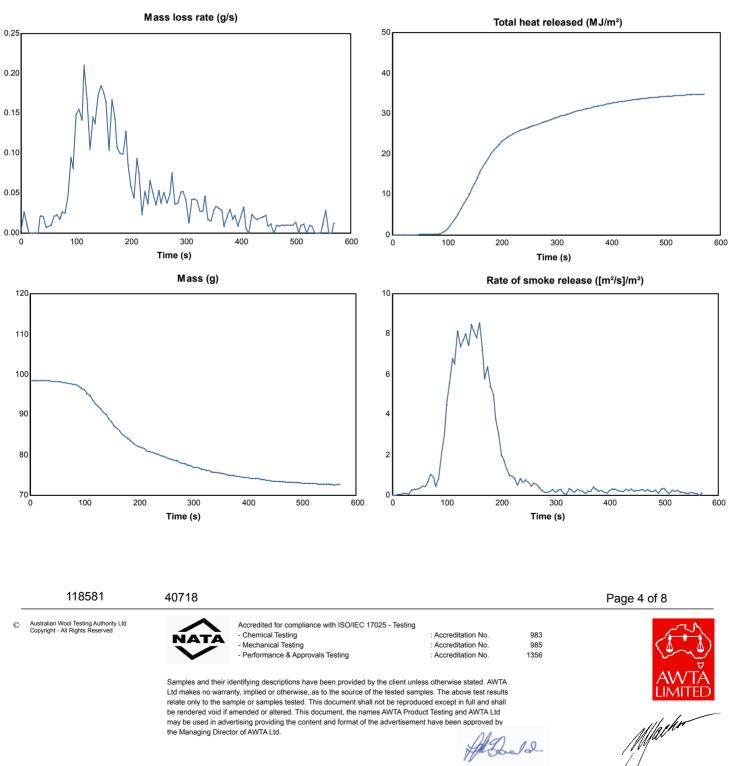

APPROVED SIGNATORY

AWTA Product Testing

Australian Wool Testing Authority Ltd - trading as AWTA Product Testing A.B.N 43 006 014 106 1st Floor, 191 Racecourse Road, Flemington, Victoria 3031

P.O Box 240, North Melbourne, Victoria 3051


Phone (03) 9371 2400 Fax (03) 9371 2499

### **TEST REPORT**

Woven Image Pty Ltd Client : 37-39 Chard Road Brookvale NSW 2100

19-006865 Test Number : Issue Date 17/12/2019 • **Print Date** 18/12/2019 :

2 Specimen :

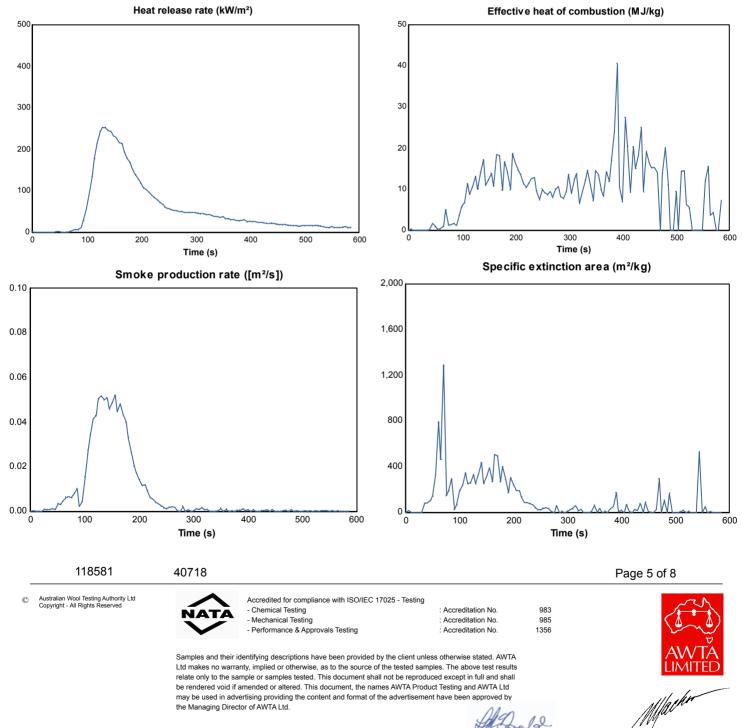

JACKSON B.Sc.(Hons) ANAGING DIRECTOR

Australian Wool Testing Authority Ltd - trading as AWTA Product Testing A.B.N 43 006 014 106 1st Floor, 191 Racecourse Road, Flemington, Victoria 3031

P.O Box 240, North Melbourne, Victoria 3051


Phone (03) 9371 2400 Fax (03) 9371 2499

### **TEST REPORT**

Client : Woven Image Pty Ltd 37-39 Chard Road Brookvale NSW 2100 
 Test Number
 :
 19-006865

 Issue Date
 :
 17/12/2019

 Print Date
 :
 18/12/2019

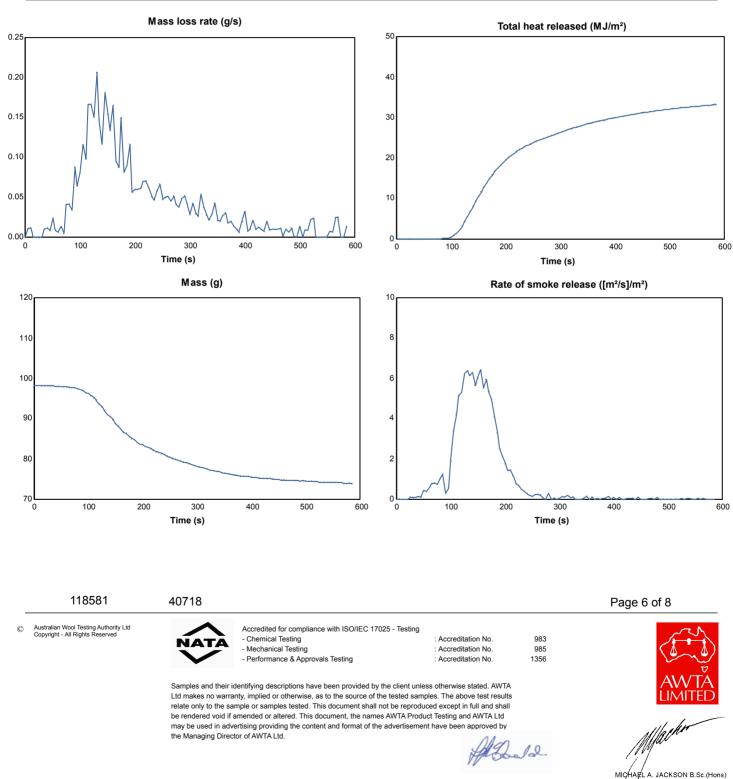

APPROVED SIGNATORY

ANAGING DIRECTOR

Australian Wool Testing Authority Ltd - trading as AWTA Product Testing A.B.N 43 006 014 106 1st Floor, 191 Racecourse Road, Flemington, Victoria 3031

P.O Box 240, North Melbourne, Victoria 3051

Phone (03) 9371 2400 Fax (03) 9371 2499


### **TEST REPORT**

Client : Woven Image Pty Ltd 37-39 Chard Road Brookvale NSW 2100 
 Test Number
 :
 19-006865

 Issue Date
 :
 17/12/2019

 Print Date
 :
 18/12/2019

Specimen: 3

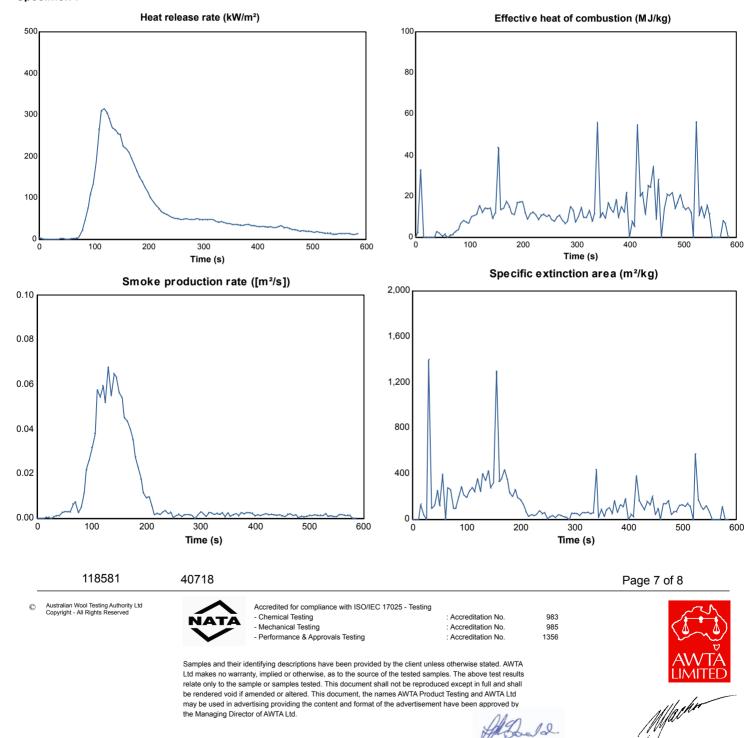

JACKSON B.Sc.(Hons)

ANAGING DIRECTOR

Australian Wool Testing Authority Ltd - trading as AWTA Product Testing A.B.N 43 006 014 106 1st Floor, 191 Racecourse Road, Flemington, Victoria 3031


P.O Box 240, North Melbourne, Victoria 3051

Phone (03) 9371 2400 Fax (03) 9371 2499

## **TEST REPORT**

Woven Image Pty Ltd Client : 37-39 Chard Road Brookvale NSW 2100

19-006865 Test Number : Issue Date 17/12/2019 • **Print Date** 18/12/2019 :

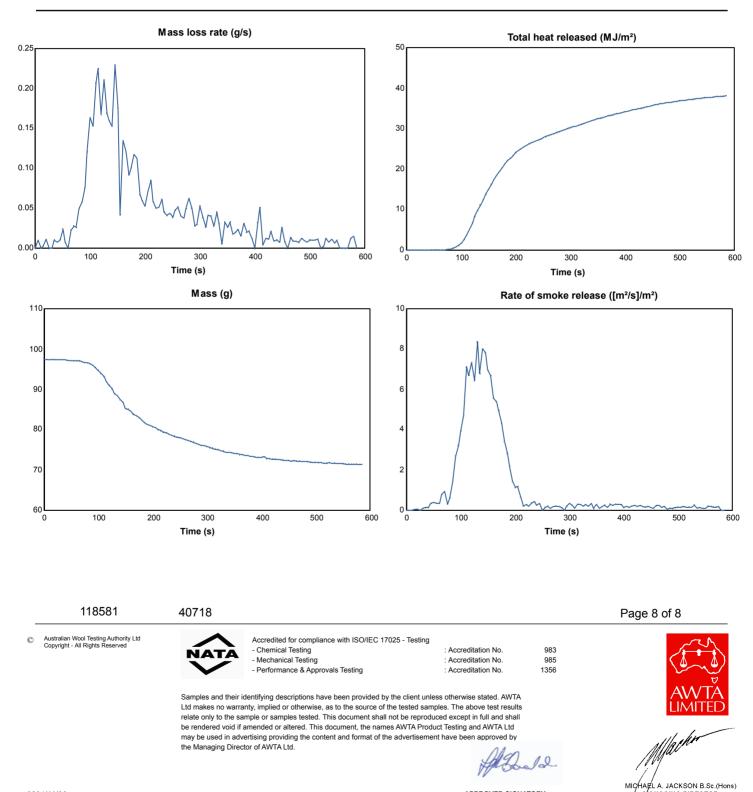

ANAGING DIRECTOR



Australian Wool Testing Authority Ltd - trading as AWTA Product Testing A.B.N 43 006 014 106 1st Floor, 191 Racecourse Road, Flemington, Victoria 3031 P.O Box 240, North Melbourne, Victoria 3051 Phone (03) 9371 2400 Fax (03) 9371 2499

### **Group Number Assessment**

(In accordance with AS 5637.1-2015)

This is to confirm that the product as described below has been tested by AWTA Product Testing .

Testing was performed in accordance with AS/NZS 3837-1998 Method of test for heat and smoke release rates for materials and products using an oxygen consumption calorimeter.

Test Sponsor :	Woven Image Pty Ltd	Test Number	:	19-006865
	37-39 Chard Road	Issue Date	:	17/12/2019
	Brookvale NSW 2100	Print Date	:	18/12/2019

Sponsor Product	Clients Ref : "Wave Dune" Non-woven acoustic wallcovering
	Colour : Off White End Use : Wallcovering
	Nominal Composition : 100% Polyester (45% Recycled) Nominal Mass per Unit Area/Density : Approx 1378g/m2
	Nominal Thickness : Approx 3mm

Product Group Number Classification :		
Average Specific Extinction Area :	224.3	m²/kg

Bald

Fiona McDonald Testing Technologist

The message/document(s) contained in this electronic attachment is intended for the party to which it is addressed and may contain confidential information or be subject to professional privilege. It's transmission is not intended to place the contents into the public domain.

If you have received this transmission in error, it's disclosure or copying is prohibited. Please contact us by collect call so that arrangements can be made at our expense to rectify the error.